

www.assuredtesting.com  
388 Servidea Drive  
Ridgway, PA 15853 USA  
P: +1 814-773-3224  
F: +1 814-773-3225

**Customer:** Basecrete Technologies  
**Purchase Order#** 855463  
**Quote #:** 011922BCT  
**Primary Contact:** Vito Mariano

**BILL TO:** FLSARASOT--2835  
Basecrete Technologies  
6148 Clark Center Ave  
Sarasota FL 34238  
USA  
Ph: 941.879.4600

**SENT TO:** FLSARASOT--2835  
Basecrete Technologies  
6148 Clark Center Ave  
Sarasota FL 34238  
USA  
Ph: 941.879.4600

# TEST REPORT - 32410

Entry Date: Friday, January 28, 2022

*Pull Off Adhesion IAW ASTM D4541 (2017), Method E, Type 4.  
Base layer is black, middle layer is gray and top layer is blue.*


See attached photos.

## Part and Test Information

<h3>Test Result</h3> <p>Results: See below.</p> <p>Sample 1:</p> <ol style="list-style-type: none"> <li>511 psi - 100% topcoat removal with cohesive gray</li> <li>669 psi - 100% topcoat removal with cohesive gray</li> <li>793 psi - 100% topcoat removal with slight cohesive gray</li> </ol> <p>Sample 2:</p> <ol style="list-style-type: none"> <li>592 psi - 100% topcoat removal with cohesive gray</li> <li>649 psi - 100% topcoat removal with cohesive gray</li> <li>482 psi - 100% topcoat removal with slight cohesive gray</li> </ol> <p>Requirements: No pass / fail criteria provided. Report results and psi.</p>	<table border="1"> <tr> <td>Test Name/Procedure</td> <td>Adhesion ASTM D4541-17 Method E Pull-off Strength</td> </tr> <tr> <td>Requirement Specification</td> <td>Unspecified</td> </tr> <tr> <td>Customer Material Specification</td> <td></td> </tr> <tr> <td>Part Number</td> <td></td> </tr> <tr> <td>Lot Number</td> <td></td> </tr> <tr> <td>Sample Description</td> <td>9.5" x 16" cement samples</td> </tr> <tr> <td>In Date</td> <td>03-Feb-22</td> </tr> <tr> <td>Out Date</td> <td>04-Feb-22</td> </tr> <tr> <td>Test Count</td> <td>2</td> </tr> <tr> <td>Return Count</td> <td>2</td> </tr> <tr> <td>Cycles</td> <td>Hours</td> </tr> <tr> <td>Required</td> <td>Required</td> </tr> <tr> <td>Hours/Cycle</td> <td>Completed</td> </tr> <tr> <td>Completed</td> <td></td> </tr> </table>	Test Name/Procedure	Adhesion ASTM D4541-17 Method E Pull-off Strength	Requirement Specification	Unspecified	Customer Material Specification		Part Number		Lot Number		Sample Description	9.5" x 16" cement samples	In Date	03-Feb-22	Out Date	04-Feb-22	Test Count	2	Return Count	2	Cycles	Hours	Required	Required	Hours/Cycle	Completed	Completed	
	Test Name/Procedure	Adhesion ASTM D4541-17 Method E Pull-off Strength																											
	Requirement Specification	Unspecified																											
	Customer Material Specification																												
	Part Number																												
	Lot Number																												
	Sample Description	9.5" x 16" cement samples																											
	In Date	03-Feb-22																											
	Out Date	04-Feb-22																											
	Test Count	2																											
	Return Count	2																											
	Cycles	Hours																											
	Required	Required																											
Hours/Cycle	Completed																												
Completed																													

Michele Singer

Assistant Laboratory Manager




Issue Date: 2/10/2022

End Of Report

Test results apply only to the item(s) as received and as tested. If Assured Testing Services needs to manipulate a test item dimensionally for the purpose of equipment parameters the results only apply to the portion that is tested. When Information supplied by the customer could affect test results, the customer is responsible for the determining validity of the reported results. Information and statements in this report are derived from material, information, and/or specifications furnished by the client and exclude any expressed or implied warranties as to the fitness of material tested or analyzed for any particular purpose or use. This report is confidential property of our client and may not be used for advertising purposes. This report shall not be reproduced except in full, without written approval of this laboratory. This recording of false, fictitious or fraudulent statements or entries on this document may be punished as a felony. Sample remnants are retained for a minimum of 6 months following issuance of test results, at which point they will be discarded unless notified in writing by the client. Any client claims or damages arising from the use of information in this report are strictly limited to the cost of the services provided by Assured Testing Services.

Revision: 8/6/2019

Assured Testing Services, Ridgway, PA  
TR32410 Basecrete Technologies  
Photos of 9.5" x 16" Samples tested for Pull Off Adhesion  
IAW ASTM D4541-17 Method E Type 4

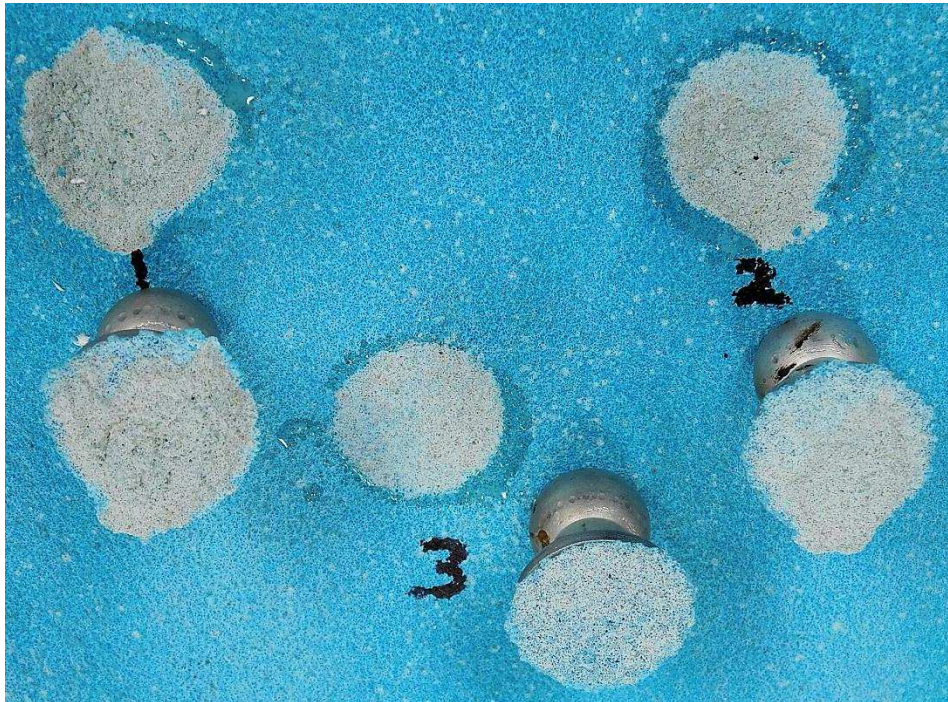

Sample 1: Three individual completed tests with corresponding dollies after pull-off adhesion – (See above)



Sample 2: Three individual completed tests with corresponding dollies after pull-off adhesion – (See above)

End of Photo Page